

Journal section: Community and Preventive Dentistry
 Publication Types: Research

doi:10.4317/jced.55278
<http://dx.doi.org/10.4317/jced.55278>

Effect of different protective agents on enamel erosion: An *in vitro* investigation

Marco Colombo ¹, Alberto Dagna ¹, Giulia Moroni ¹, Marco Chiesa ¹, Claudio Poggio ¹, Giampiero Pietrocola ²

¹ Department of Clinical-Surgical, Diagnostic and Pediatric Sciences, Section of Dentistry, University of Pavia, Pavia, Italy

² Department of Molecular Medicine, Unit of Biochemistry, University of Pavia, Pavia, Italy

Correspondence:

Department of Clinical, Surgical
 Diagnostic and Pediatric Sciences
 Section of Dentistry, Policlinico "San Matteo"
 Piazzale Golgi 3, 27100 Pavia, Italy
claudio.poggio@unipv.it

Colombo M, Dagna A, Moroni G, Chiesa M, Poggio C, Pietrocola G. Effect of different protective agents on enamel erosion: An *in vitro* investigation. J Clin Exp Dent. 2019;11(2):e113-8.
<http://www.medicinaoral.com/odo/volumenes/v11i2/jcedv11i2p113.pdf>

Received: 07/09/2018
 Accepted: 07/01/2019

Article Number: 55278	http://www.medicinaoral.com/odo/indice.htm
© Medicina Oral S. L. C.I.F. B 96689336 - eISSN: 1989-5488	
eMail: jced@jced.es	
Indexed in:	
Pubmed	
Pubmed Central® (PMC)	
Scopus	
DOI® System	

Abstract

Background: The purpose of this *in vitro* study was to compare the effect of different protective agents on enamel erosion by measuring mean percentage weight loss.

Material and Methods: Extracted teeth were sectioned into uniform slabs and enamel specimens were randomly distributed to different groups. Initial weight of all enamel specimens was registered. The protective agents used in this study were Tooth Mousse, MI Paste Plus, Remin Pro and Remin Pro Forte. A control group was treated just with tap water. All the specimens were immersed in Coca-Cola for a total of 8 min at room temperature, dried and weighed. Enamel dissolution caused by acidic soft drink was analyzed: specimens were weighed after each immersion period and mean percent weight loss was calculated. Weight loss data were subjected to Analysis of Variance (One-way ANOVA) followed by Bonferroni's post hoc tests.

Results: All the groups showed a statistically significant loss of weight ($p < 0.01$) during the testing periods, increased after 8 days (~55%) and 12 days (~70%) of exposure. Specimens treated with protective agents showed significantly lower % of weight loss especially with Remin Pro or Remin Pro Forte.

Conclusions: Soft drinks can cause enamel erosion, but protective agents tested may enhance enamel resistance against erosion.

Key words: Enamel, erosion, protective agents, soft drinks, toothpastes.

Introduction

Dental erosion is a process involving the dissolution of enamel and dentine by non-bacterial acids that soften the enamel surface, so mechanical factors such as abrasion and attrition may result in further loss of tooth tissue (1). The prevalence of dental erosion is thought to be increasing, due to the wide availability and frequent consumption of acidic drinks such as soft drinks, sports drinks and fruit juices (2). The development of erosion involves

a chemical process in which the inorganic phase of the tooth is demineralized, thereby reducing the hardness of tooth substrates (3). Typical acid sources come from the diet, medications, occupational exposure, and lifestyle activities (4,5).

Many strategies have been established to prevent dental erosion (6). Toothpastes were considered effective and affordable vehicles to enhance enamel and dentin resistance (7) and the incorporation of protective agents

in toothpastes has become increasingly common. Dental sensitivity is a problem often related to acid erosion and a common complaint among patients. Currently, conventional fluoride-based toothpastes do not seem to be able to effectively protect teeth against erosion (8). Recently, new toothpastes formulations have been introduced to contrast enamel and dentin erosion (9). Among the large amount of commercially available products, several new toothpaste technologies were subject of our previous studies (10,11). The casein phosphopeptides amorphous calcium phosphate CPP-ACP solutions have also been shown to significantly remineralize enamel subsurface lesions *in vitro* (12). CPP-ACP has been successfully incorporated into oral health products such as mouthrinses, sugar-free chewing gums and sports drinks to reduce enamel erosion (13). It has been suggested that casein phosphopeptide-amorphous calcium phosphate with fluoride (CPP-ACPF) provide additional fluoride along with calcium and phosphate ions for remineralization of enamel (14).

Fluoride and stannous ions have shown anti-erosive action *in vitro* and *in situ* (15). Topical application of fluoridated rinses (112–450 ppm F, as NaF) may protect against erosive tooth wear (16) by forming a CaF₂ or CaF₂-like layer on the enamel surface. Similarly, stannous ion-containing rinses (800 ppm Sn, as SnF₂ or SnCl₂) seem to prevent dental erosion by depositing a stable acid-resistant layer on the tooth surfaces (17,18). Sn-containing rinses may also react with dental hard tissues, due to the low pH, leading to the incorporation of the Sn ion into the enamel, thereby creating a more acid-resistant substrate (19).

The purpose of this *in vitro* study was to compare the effect of different protective agents on enamel erosion, measuring mean percentage weight loss before and after acidic beverage exposure.

Material and Methods

Freshly extracted and sound human permanent incisors were used for this study. Inclusion criteria were: no hypo calcification, no caries, no macroscopic fractures. The teeth were carefully cleaned from calculus and debris and stored in a 1% Chloramine-T solution

(Fisher Chemical, Fair lawn, NJ, USA) consisting of 12% active chlorine diluted in distilled water. The crown of each tooth was removed at cementum-enamel junction utilizing a straight fissure carbide bur mounted on a high-speed water-cooled handpiece. One transversal section of 2-mm thickness was obtained from the facial surface of each crown using a pre-programmed automatic Accutom-50 diamond cutter (Accutom Hard Tissue Microtome, Struers, Ballerup, Denmark). Each slice was then sectioned in two sections, obtaining a total of two samples. Enamel specimens were catalogued and stored into distilled water at room temperature.

Initial weight of each enamel specimen was registered: all specimens were dried on blotting paper at room temperature for one hour and weighed using a precision balance (Mettler-Toledo, model AE1633, Novate Milanese, Italy, metering accuracy 0.01 mg).

The samples were randomly attributed to 5 groups (n=10). Specimens of group 1 were treated only with tap water (control). Tap water (pH 7.20) was chosen as a negative control because it was expected to have no or minimal demineralization effect on enamel.

Specimens of groups 2, 3, 4, 5 were treated with application of protective pastes onto the surface without brushing for 3 min at 0, 8, 24, 32 h (Fig. 1). Four different protective pastes (Tooth Mousse, MI Paste Plus, Remin Pro and Remin Pro Forte) were evaluated. The characteristics, chemical composition and manufacturer of the tested products are reported in Table 1. All the treated samples were weighed using the same precision balance and no statistically significant differences in term of weight variation before or after protective pastes application were found ($p>0.05$, ANOVA with Bonferroni post hoc test).

Thereafter, all specimens were simultaneously placed in a PVC pannier suspended in a plastic container with 6 ml of a soft drink (Coca-Cola, The Coca-Cola Company, Milano, Italy) and immersed for 2 min at room temperature, then rinsed with deionized water. Four consecutive intervals of immersion procedure were carried out for a total of 8 minutes (20). Each specimen was removed from the soft drink using tweezers, dried with blotting paper, left at room temperature to dry for 60 minutes,

								3 min at 0, 8, 16, 24, 32h		at 32h		24h			
Group 1	ENAMEL	→	WEIGHT	→	WATER	→	WEIGHT	→	tap water (control)	→	WEIGHT	→	SOFT DRINK	→	WEIGHT
Group 2	ENAMEL	→	WEIGHT	→	WATER	→	WEIGHT	→	Tooth Mousse	→	WEIGHT	→	SOFT DRINK	→	WEIGHT
Group 3	ENAMEL	→	WEIGHT	→	WATER	→	WEIGHT	→	MI Paste Plus	→	WEIGHT	→	SOFT DRINK	→	WEIGHT
Group 4	ENAMEL	→	WEIGHT	→	WATER	→	WEIGHT	→	Remin Pro	→	WEIGHT	→	SOFT DRINK	→	WEIGHT
Group 5	ENAMEL	→	WEIGHT	→	WATER	→	WEIGHT	→	Remin Pro Forte	→	WEIGHT	→	SOFT DRINK	→	WEIGHT

Fig. 1: Diagram of the study design.

Table 1: Protective materials used in this study.

Group	MATERIAL	MANUFACTURER	CHEMICAL COMPOSITION	BATCH NUMBER
1	tap water	N/A	Water, various minerals	N/A
2	Tooth Mousse	GC Europe N.V Leuven, Belgium	Glycerol, CPP-ACP, D-Sorbitol, CMC-Na, Propylene Glycol, Silicon dioxide, Titanium dioxide, Xylitol, Phosphoric acid, Flavoring, Zinc oxide, Sodium saccharin, Ethyl p-hydroxybenzoate, Magnesium oxide, Guar gum, Propyl p-hydroxybenzoate, Butyl p-hydroxybenzoate. 900 ppm fluoride.	150423M
3	MI Paste Plus	GC Europe N.V Leuven, Belgium	CPP-ACPF* (Casein Phosphopeptide -Amorphous Calcium Phosphate Fluoride), Glycerol, D-Sorbitol, CMC-Na, Propylene glycol, Silicon dioxide, Titanium dioxide, Xylitol, Phosphoric acid, Flavoring, Sodium saccharin, Ethyl p-hydroxybenzoate, Propyl p-hydroxybenzoate, Butyl p-hydroxybenzoate. 900 ppm fluoride. *Recaldent	150609M
4	Remin Pro	Voco GmbH Cuxhaven, Germany	Hydroxy apatite, sodium fluoride (1450 ppm fluoride), xylitol	1502025
5	Remin Pro Forte	Voco GmbH Cuxhaven, Germany	Hydroxy apatite, sodium fluoride (1450 ppm fluoride), xylitol, ginger and curcuma extracts	419551019

and weighed. The mass loss was calculated as a percentage of the results obtained before the application of protective pastes or tap water (mass set to 0%). Continuous data were expressed as means and standard deviations. Weight loss data were subjected to Analysis of Variance (One-way ANOVA) followed by Bonferroni's post hoc tests. Analyses were performed using Prism 4.0 (Gra-

phPad). Two-tailed *P* values of 0.05 were considered statistically significant.

Results

Results are shown in Fig. 2 and in Table 2. The acidic soft drink Coca-Cola caused ~25% of weight loss of enamel after 4 days of exposure. The weight loss of ena-

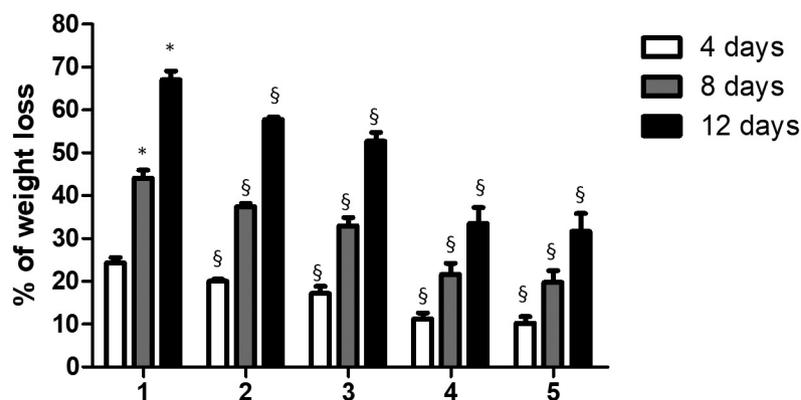


Fig. 2: Relation between weight loss of enamel teeth specimens and time. The mass loss was calculated as a percentage of that observed prior the protective pastes or water (control) application (mass set to 0%). The reported data are the mean values (+/- SD). Symbol (*) indicates statistically significant differences ($p < 0.01$) in group 1 as determined by repeated-measures one-way ANOVA with a Bonferroni's post hoc tests. Symbol (\$) indicates statistically significant differences ($p < 0.01$) between group 1 and towards each other group as determined by repeated-measures one-way ANOVA with a Bonferroni's post hoc tests.

Table 2: Mean (\pm SD) of the enamel weight loss for different groups. The mass loss was calculated as a percentage of that observed prior the protective pastes or water (control) application (mass set to 0%).

Group	Time (days)		
	4	8	12
1	24,32 \pm 2,83	44,12 \pm 4,07	67,02 \pm 4,72
2	20,06 \pm 1,05	37,44 \pm 1,67	57,78 \pm 1,38
3	17,18 \pm 3,71	32,98 \pm 4,36	52,7 \pm 4,64
4	11,26 \pm 3,02	21,66 \pm 5,80	33,5 \pm 8,37
5	10,24 \pm 3,35	19,8 \pm 6,02	31,62 \pm 9,35

mel significantly increased of \sim 55% and \sim 70% after 8 and 12 days of exposure respectively.

As shown in Fig. 2, Tooth Mousse and MI Paste Plus showed a similar trend in terms of weight loss of enamel. In both cases and for all the exposure times to Coca-Cola evaluated, the % of weight loss was significantly lower than that observed for control group ($P < 0.01$). For all the tested times, specimens treated with Remin Pro or Remin Pro Forte, showed significantly lower % of weight loss compared to the control group ($P < 0.01$) or both groups 2 and 3 ($P < 0.01$).

Discussion

Surface roughness increase of enamel due to exposure to non-alcoholic soft drinks such as Coca-Cola has been well documented (21,22). This study aimed to explore if exposure to Coca-Cola after the treatment with protective agents caused the same loss of enamel, in order to evaluate if protective pastes have preventive effect on enamel erosion.

As previously stated, several factors play important roles in the potential destruction of tooth structure following exposure to soft drinks and to other sweetened beverages (23). Salivary pH lies within a range of 5.5 to 6.5, with a pH of 5.5 or below, accepted as a threshold level for destruction of tooth structure, i.e. caries and erosion (24). A sustained low salivary pH (< 5.5) has been shown to be a result of intake of carbohydrates or sugars (sucrose, fructose), and acids (phosphoric, citric, and other organic acids) (25). These ingredients decrease the buffering capacity (of saliva) and maintain the oral pH below the threshold level (5.5 pH) necessary for alteration of enamel (26). A constant assault by acids or incorrect drinking habits can result in accelerated demineralization of the enamel (and dentin) surface (27). Phosphoric, citric acid and/or citrates found in many soft drinks are added as flavoring agents or acidulants, and can concurrently chelate to calcium, promoting a decreased buffering effect of saliva and thus increased tooth destruction (23,24). Presence of calcium, phosphorous and fluoride in soft drinks or fruit juices has been shown to be limiting factor of the erosion potential in the oral cavity (28,29).

According to Hemingway *et al.*, (30) with the higher

concentration of calcium ions found in soft drinks, the less likely the enamel surface calcium ions will be detached. Another study by Low *et al.* (31) found a direct relationship between the weight loss of tooth enamel and loss of calcium ions. Still yet another study by Davis *et al.* (32) has indicated that the erosive potential occurs in the first few minutes following exposure and is a factor of the beverage pH. Other investigations(32-34), evaluating the erosive potential of various beverages on permanent tooth structure revealed that Coca-Cola caused increased percent weight loss of the enamel specimens compared to Diet Coke. This finding suggests that beverages such as Coca-Cola, supplemented with refined carbohydrates or sugars (sucrose, high fructose corn syrup), compared to artificial sweeteners found in diet versions of the same beverage, may be contributing factors to tooth dissolution.

The results of the present study suggest the potential harmful effects of the tested beverage could be especially pertinent to persons with systemic conditions (Sjögrens syndrome) or to athletes, whereby salivary flow is reduced or non-existent causing xerostomia or dry-mouth conditions, because *in vitro* conditions of the oral environment cannot be replicated (35). Human saliva contains hundreds of proteins that serve as protective factors. Saliva also serves as a buffering agent, diluent, and repository of calcium and phosphate for remineralization - limiting the erosive potential associated with soft drink consumption (36,37).

The characteristics, chemical composition and manufacturer of the protective agents tested (Tooth Mousse, MI Paste Plus, Remin Pro, Remin Pro Forte) are reported in Table 1. Remin Pro and Remin Pro Forte are toothpastes containing Hydroxyapatite, sodium fluoride (1450 ppm fluoride) and xylitol. Tooth Mousse and MI Paste Plus are remineralizing agents based on casein phosphopeptide-stabilized amorphous calcium phosphate complexes (CPP-ACP) and casein phosphopeptide-stabilized amorphous calcium fluoride phosphate complexes (CPP-ACFP). The ability of casein to stabilize calcium and phosphate ions resides in sequences that can be released as small peptides (case in phosphopeptides) by partial enzymic digestion. The CPP-ACP and CPP-ACFP complexes have been incorporated into dental creams and

stabilize or deliver bioavailable calcium, phosphate and fluoride ions (14). The softened enamel caused by soft drink, which represented the early stage of erosion, became hardened after four application of a CPP-ACP paste (20).

A significant challenge was the differing composition and concentrations of fluoride in the pastes. The results of this *in vitro* model demonstrated that the highly concentrated fluoride agents may protect the enamel. Remin Pro (1450 ppm) and in Remin Pro Forte (1450 ppm) have the highest concentration of fluoride, whilst MI Paste Plus (900 ppm) and Tooth Mousse (0 ppm) have considerably less.

Percent weight loss of specimens exposed to early stages in Coca-Cola showed linear progression with time. Remin Pro and Remin Pro Forte recorded the lowest values of weight loss after immersion in Coca Cola. This means that these pastes make the enamel resistant to acid attack effectively. Compared to the control group 1, the results of the specimens treated with all protective paste are statistically significant ($p < 0.01$). For all the tested times, specimens treated with Remin Pro or Remin Pro Forte, showed significantly loss of weight compared to the other groups, maybe thanks to their high concentration in fluoride.

Conclusions

Within the limitations of this *in vitro* study this study, all tested protective agents showed preventive effect against acidic action of soft drinks. Remin Pro and Remin Pro Forte showed better results than Tooth Mousse and MI Paste Plus. This difference in enamel protection is due to the different concentration of fluoride, which shows that fluoride can afford protection of enamel against erosion. This study indicated that enamel is susceptible to erosion of soft drinks, but protective toothpaste can defend it against acidic erosion in different way according to their composition.

References

- Lewis R, Dwyer-Joyce RS. Wear of human teeth: a tribological perspective. Institution of Mechanical Engineers Part J-Journal of Engineering Tribology. 2005;219:1-18.
- Lussi A, Hellwig E, Zero D, Jaeggi T. Erosive tooth wear: diagnosis, risk factors and prevention. Am J Dent. 2006;19:319-25.
- Lussi A, Schlueter N, Rakhmatullina E, Ganss C. Dental Erosion - an overview with emphasis on chemical and histopathological aspects. Caries Res. 2011;45: 2-12.
- Lussi A, Jaeggi T, Zero. The role of diet in the aetiology of dental erosion. Caries Res. 2004;38:34-44.
- Barbour ME, Finke M, Parker DM, Hughes JA, Allen GC, Addy M. The relationship between enamel softening and erosion caused by soft drinks at a range of temperatures. J Dent. 2007;34:207-13.
- Magalhães AC, Wiegand A, Rios D, Honório HM, Buzalaf MA. Insights into preventive measures for dental erosion. J Appl Oral Sci. 2009;17:75-86.
- Kato MT, Lancia M, Sales-Peres SH, Buzalaf MA. Preventive effect of commercial desensitizing toothpastes on bovine enamel erosion in vitro. Caries Res. 2010;44:85-9.

- Moron BM, Miyazaki SS, Ito N, Wiegand A, Vilhena F, Buzalaf MA, et al. Impact of different fluoride concentrations and pH of dentifrices on tooth erosion/abrasion in vitro. Aust Dent J. 2013;58:106-11.
- Ganss C, Schulze K, Schlueter N. Toothpaste and erosion. Monogr Oral Sci. 2013;23:88-99.
- Lombardini M, Ceci M, Colombo M, Bianchi S, Poggio C. Preventive effect of different toothpaste on enamel erosion: AFM and SEM studies. Scanning. 2014;36:401-10.
- Poggio C, Lombardini M, Vigorelli P, Ceci M. Analysis of Dentin/Enamel Remineralization by a CPP-ACP Paste: AFM and SEM Study. Scanning. 2013;35:366-74.
- Hegde MN, Moany A. Remineralization of enamel subsurface lesions with casein phosphopeptide-amorphous calcium phosphate: A quantitative energy dispersive X-ray analysis using scanning electron microscopy: An in vitro study. J Conserv Dent. 2012;15:61-7.
- Adebayo OA, Burrow MF, Tyas MJ. An SEM evaluation of conditioned and bonded enamel following carbamide peroxide bleaching and casein phosphopeptide amorphous calcium phosphate (CPP-ACP) treatment. J Dent. 2007;37:297-306.
- Cochrane NJ, Cai F, Huq NL, Burrow MF, Reynolds EC. New approaches to enhanced remineralization of tooth enamel. J Dent Res. 2010;89:1187-97.
- Magalhães AC, Wiegand A, Rios D, Buzalaf MA, Lussi A. Fluoride in dental erosion. Monogr Oral Sci. 2011;22:158-70.
- Gracia L, Rees G, Brown A and Fowler C. An in vitro evaluation of a novel high fluoride daily mouthrinse using a combination of microindentation, 3D profilometry and DSIMS. J Dent. 2010;38:12-20.
- Ganss C, Neutard L, von Hinckeldey J, Klimek J and Schlueter N. Efficacy of a tin/fluoride rinse: a randomized in situ trial on erosion. J Dent Res. 2010;89:1214-8.
- Ganss C, Schlueter N, Hardt M, Schattenberg P and Klimek J. Effect of fluoride compounds on enamel erosion in vitro: a comparison of amine, sodium and stannous fluoride. Caries Res. 2008;42:2-7.
- Schlueter N, Klimek J and Ganss C. In vitro efficacy of experimental tin- and fluoride-containing mouth rinses as anti-erosive agents in enamel. J Dent. 2009;37:944-8.
- Tantbirojin D, Huang A, Ericson MD, Poolthong S. Change in surface hardness of enamel by a cola drink and a CPP-ACP paste. J Dent. 2008;36:74-9.
- Owens BM, Mallette JD and Phebus JG. Effects of Carbonated Cola Beverages, Sports and Energy Drinks and Orange Juice on Primary and Permanent Enamel Dissolution. Austin J Dent. 2014;1:1004-10.
- Barac R, Gasic J, Trutic N, Sunaric S, Popovic J, Djekic P, et al. Erosive Effect of Different Soft Drinks on Enamel Surface in vitro: Application of Stylus Profilometry. Med Princ Pract. 2015;24:451-7.
- Tahmassebi JF, Duggal MS, Malik-Kotru G, Curzon ME. Soft drinks and dental health: a review of the current literature. J Dent. 2006;34:2-11.
- Anderson P, Hector MP, Rampersad MA. Critical pH in resting and stimulated whole saliva in groups of children and adults. Int J Paediatr Dent. 2001;11:266-73.
- Edwards M, Creanor SL, Foye RH, Gilmour WH. Buffering capacities of soft drinks: the potential in uence on dental erosion. J Oral Rehabil. 1999;26:923-7.
- Davani R, Walker J, Qian F, Wefel JS. Measurement of viscosity, pH, and titratable acidity of sports drinks. J Dent Res. 2003;82(special issue A):326.
- Jensdottir T, Holbrook P, Nauntofte B, Buchwald C, Bardow A. Immediate erosive potential of cola drinks and orange juices. J Dent Res. 2006;85:226-30.
- Davis RE, Marshall TA, Qian F, Warren JJ, Wefel JS. In vitro protection against dental erosion afforded by commercially available, calcium-fortified 100 percent juices. J Am Dent Assoc. 2007;138:1593-8.
- Barbour ME, Shellis RP, Parker DM, Allen GC, Addy M. Inhibition of hydroxyapatite dissolution by whole casein: the effects of pH, protein concentration, calcium, and ionic strength. Eur J Oral Sci. 2008;116:473-8.
- Hemingway CA, Parker DM, Addy M, Barbour ME. Erosion of

- enamel by non-carbonated soft drinks with and without toothbrushing abrasion. *Br Dent J.* 2006; 201: 447-50.
31. Low IM, Alhuthali A. In-situ monitoring of dental erosion in tooth enamel when exposed to soft drinks. *Mater Sci Engineer.* 2008;28:1322-5.
32. Von Fraunhofer JA, Rogers MM. Dissolution of dental enamel in soft drinks. *Gen Dent.* 2004;52:308-12.
33. Jain P, Nihill P, Sobkowski J, Agustin MZ. Commercial soft drinks: pH and in vitro dissolution of enamel. *Gen Dent.* 2007;55:150-4.
34. Ehlen LA, Marshall TA, Qian F, Wefel JS, Warren JJ. Acidic beverages increase the risk of in vitro tooth erosion. *Nutr Res.* 2008;28:299-303.
35. Stewart CM, Berg KM, Cha S, Reeves WH. Salivary dysfunction and quality of life in Sjögren syndrome: a critical oral-systemic connection. *J Am Dent Assoc.* 2008;139: 291-9.
36. Hara AT, González-Cabezas C, Creeth J, Zero DT. The effect of human saliva substitutes in an erosion-abrasion cycling model. *Eur J Oral Sci.* 2008;116:552-6.
37. Buzalaf MA, Hannas AR, Kato MT. Saliva and dental erosion. *J Appl Oral Sci.* 2012;20: 493-502.

Conflicts of Interest

The authors have declared that no conflict of interest exist.