

Journal section: Orthodontics

Publication Types: Research

doi:10.4317/jced.55719

<http://dx.doi.org/10.4317/jced.55719>

Influence of delay between dental bleaching with 35% hydrogen peroxide and orthodontic brackets on the bond strength at the enamel/adhesive interface

Antônio-Augusto-Lima de Almeida ¹, Darlon-Martins Lima ², Adriana-de Fátima-Vasconcelos Pereira ², Soraia-de Fátima-Carvalho Sousa ², Cláudia-Maria-Coêlho Alves ²

¹ Master of Science in Dentistry - Post-Graduate Program in Dentistry, Federal University of Maranhão, São Luís, MA, Brasil

² PhD, Post-Graduate Program in Dentistry. Federal University of Maranhão, São Luís, MA, Brasil

Correspondence:

Federal University of Maranhão
Avenida dos Portugueses, 1966
Campus Universitário do Bacanga
São Luís – MA - Brasil
C.E.P: 65080-805
cmcoelho@gmail.com

Received: 15/03/2019

Accepted: 01/04/2019

de Almeida AAL, Lima DM, Pereira AFV, Sousa SFC, Alves CMC. Influence of delay between dental bleaching with 35% hydrogen peroxide and orthodontic brackets on the bond strength at the enamel/adhesive interface. J Clin Exp Dent. 2019;11(5):e447-51.

<http://www.medicinaoral.com/odo/volumenes/v11i5/jcedv11i5p447.pdf>

Article Number: 55719 <http://www.medicinaoral.com/odo/indice.htm>
© Medicina Oral S. L. C.I.F. B 96689336 - eISSN: 1989-5488
eMail: jced@jced.es

Indexed in:

Pubmed
Pubmed Central® (PMC)
Scopus
DOI® System

Abstract

Background: The aim of this study was to evaluate the influence of waiting time between the bleaching with 35% hydrogen peroxide and orthodontic brackets bonding on shear bond strength (SBS) in enamel.

Material and Methods: Eighty bovine teeth were randomly divided into four groups (G): G1(negative control) and G2, G3 and G4 (experimental groups). The experimental groups were submitted to bleaching. Prior to orthodontic brackets bonding to enamel the procedure was adopted different waiting times, as follows: G2 (1 day); G3 (7 days) and G4 (14 days). It was performed enamel etching (30s), washing water (30s), application of adhesive system followed by photoactivation (20s). A thin layer of composite resin was placed between the adhesive and the brackets. The applied pressure was measured by tensiometer (300N/40s). The composite resin was light-cured (40s). After 24 hours the shear test was held (0.5mm/min). To compare the SBS it was used ANOVA one-way followed by Tukey test ($\alpha = 0.05$). The Adhesive Remaining Index (ARI) was analyzed using the Kruskal-Wallis test.

Results: The SBS values were significantly lower in G2 (15.51 MPa) and G3 (17.77 MPa) compared to G1 (30.14 MPa) and G4 (28.50 MPa) ($p < 0.05$). The ARI revealed significant difference between the G3 and the other groups ($p < 0.05$).

Conclusions: It was concluded that the bond strength in enamel in the interfaces/adhesive system/composite resin/orthodontic brackets was more effective 14 days after the bleaching with 35% hydrogen peroxide.

Key words: Dental materials, teeth bleaching, orthodontic brackets.

Introduction

Tooth bleaching has become a safe option, mainly in patients who have stained teeth due to the consumption of fluorosis or consumption of certain beverages (1). Whitening treatment can be performed at home or carried out at office (2). Home bleaching is usually done with 10 to 22%, carbamide peroxide whereas office bleaching is done with 35% hydrogen peroxide. In-office whitening is often chosen due to its advantages of convenience and speed (3). Orthodontic treatment has become a popular option among patients of all ages. Its effectiveness depends on the bonding of orthodontic brackets to enamel, among other factors. Tooth whitening can interfere with the effectiveness of adhesive procedures (3,4). Some studies suggest that patients wait at least 7 or 14 days after bleaching before undergoing bracket bonding, to ensure the restoration of normal bond strength values (3,5). Although the negative influence of bleaching on bond strength has been confirmed (6–8), there is no consensus on the ideal interval between tooth whitening and bracket bonding to obtain effective adhesion of the brackets to enamel (5,9-13). Therefore, the aim of this study was to evaluate the influence of the time interval between bleaching and bracket bonding on the shear bond strength (SBS) of orthodontic brackets bonded to enamel. The null hypothesis was that the delay after bleaching would have no influence on the SBS at the adhesive/enamel interface.

Material and Methods

-Selection and preparation of specimens

Eighty freshly extracted bovine incisors were selected for the study. All teeth had a fully formed apex and a labial surface that was free of fractures, cracks, or erosion. After cleaning, the teeth were sectioned into 5.0-mm segments at the cemento-enamel junction. They were embedded in acrylic resin (JET Classico, São Paulo, SP,

Brazil) by using a matrix from poly-vinyl chloride tubes (Tigre®, Pouso Alegre, MG, Brazil). The coronary portion of each specimen was polished with pumice (Maquira®, Maringa, PR, Brazil) and water, by using a Robson brush at low speed. Teeth were placed in saline solution for rehydration until use. Materials used in the tooth whitening and bonding procedures are presented in Table 1. Teeth were randomly divided into four groups (n = 20): G1 (negative control) and G2, G3, and G4 (experimental groups) (Fig. 1).

-Dental bleaching protocol

The negative control group (G1) received no bleaching treatment. Experimental groups (G2, G3 and G4) were subjected to bleaching with hydrogen peroxide (35% Whiteness HP®) at a 1:3 ratio of thickener to 35% hydrogen peroxide, according to the manufacturer's recommendations. The mixture was placed on the buccal surface of each specimen. After 1 minute, photoactivation was performed in three 15-minute periods. The gel was aspirated, and the tooth surface was rinsed with water. Specimens were kept in saline solution until the adhesive procedure was performed 1 day (G2), 7 days (G3) or 14 days (G4) after bleaching.

-Bonding procedure

After the experimental period, teeth were again polished as described above. A 12-mm² area at the approximate center of the tooth crown was etched with 37% phosphoric acid (Magic Acid®) for 30 seconds, followed by rinsing under running water for 30 seconds. A thin layer of adhesive (Magic Bond®) was applied with a microbrush and light-cured for 20 seconds. A thin layer of resin composite (Z350®) was inserted on the base (11.7 mm²) of a straight-wire-type bracket (Roth Light, Dental Morelli® Ltda., Jundiaí, SP, Brazil). To standardize the adhesive bonding procedure, 300 N of pressure (measured by a tensiometer) was applied to the bracket by pliers, followed by light-curing for 40 seconds. After

Table 1: Composition and manufacturer of each material used.

| Material | Composition | Manufacturer |
|---------------|--|--|
| Whiteness HP® | 35% hydrogen peroxide, thickener, red dye, glycol, and water | FGM Produtos Odontológicos, Joinville, Brazil |
| Magic Acid® | 37% phosphoric acid gel, glycerin, silicon dioxide, water, and dye | Vigodent S/A Ind. E Com., Rio de Janeiro, Brazil |
| Magic Bond® | Bis-GMA, TEGDMA, photoactivator, and stabilizer | Vigodent S/A Ind. E Com, Rio de Janeiro, Brazil |
| Filtek Z350® | Bis-GMA, UDMA, TEGDMA, Bis-EMA | 3M ESPE, São Paulo, Brazil |

Bis-GMA: bisphenylglycidyl dimethacrylate, TEGDMA: triethylene glycol dimethacrylate, UDMA: urethane dimethacrylate, Bis-EMA: ethoxylated bisphenol-A dimethacrylate.

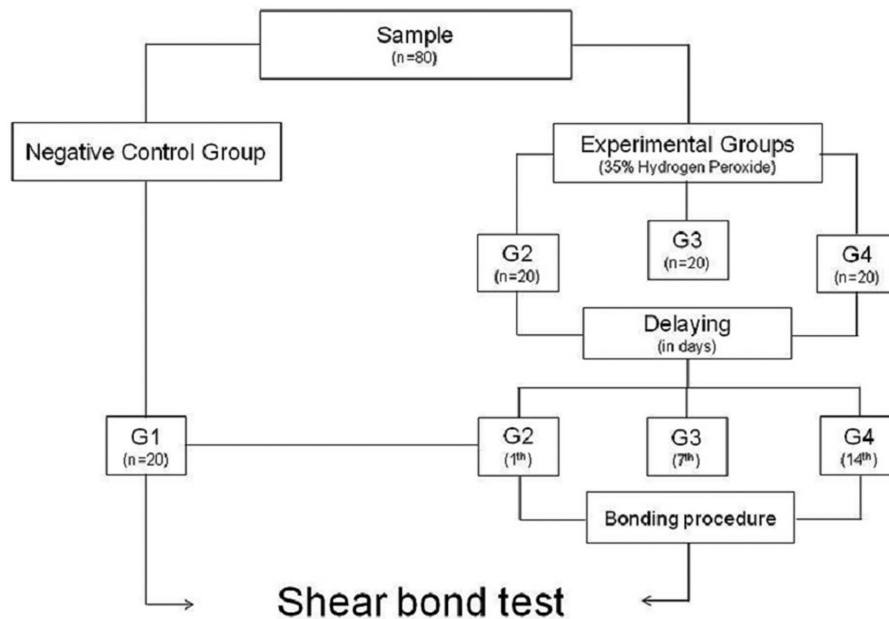


Fig. 1: Experimental design study.

bonding, all teeth were stored in saline solution for 24 hours until the shear test.

-Shear test

The shear test was carried out in an universal mechanical testing machine (Instron 3342, Canton, MA) by using a load cell of 500 N and a speed of 0.5 mm/min, according to ISO TR11405 for metallic devices. The machine recorded the maximum load at the time of fracture (recorded in N and later transformed into MPa).

-Failure mode analysis

The fracture pattern was analyzed by using a stereomicroscope (Kozo and Electronical Optical Instrumentation, Nanjing, Jiangsu, China) with a magnification of 30x. The adhesive remnant index (ARI) was scored as follows (14): score of 1 = 100% of the adhesive remaining on the enamel; score of 2 = greater than 90% of the adhesive remaining on the enamel; score of 3 = greater than 10% but less than 90% of the adhesive remaining on the enamel; score of 4 = less than 10% of the adhesive remaining on the enamel; and score of 5 = no adhesive remaining on the enamel.

-Statistical analysis

SBS values were analyzed by using one-way analysis of variance (ANOVA) followed by the Tukey test. ARI scores were compared by the Kruskal-Wallis test. All tests were performed in the SPSS for Windows (version 16.0) software package. The significance level was set at 5%.

Results

Data for the shear bond strength test (MPa) and mode of failure (ARI) are summarized in Table 2.

There was a significant difference between the means of

the bond strength of G1 and G2 ($p < 0.001$), G1 and G3 ($p = 0.02$) and G3 and G4 ($p = 0.009$).

Discussion

The null hypothesis was rejected, because the delay had influence on the bond strength of the interface adhesive system/enamel. Average SBS values of the group with bonding 1 day after bleaching (G2) were significantly lower than those of the unbleached control group (G1), consistent with results obtained in earlier studies (6,15-18). When the interval between bleaching and bonding was 7 days (G3), the SBS values were significantly lower compared to those of the unbleached control group (G1). These findings are consistent with the study of Mullins *et al.* (18), who advised that brackets be bonded 14 days after tooth whitening. However, other researchers using similar methodologies (6,19) did not find any significant in SBS values for brackets bonded at the same time intervals after bleaching. One possible reason for this difference may be the use of different materials or methodologies, such as intracoronary bleaching and antioxidant treatment (6,20).

Higher SBS values were found in G4 (bonding 14 days after bleaching), compared to G2 and G3, but not compared to G1. A delay of 7 days was insufficient to decrease the harmful effects of free oxygen from 35% hydrogen peroxide, whereas a delay of 14 days ensured acceptable safety to perform bracket bonding (15,22). However, Uysal *et al.* (21) and Bishara *et al.* (22) suggest that there was no significant reduction in the bond strength, regardless of the time since the whitening procedure. It is relevant to emphasize that the present study

Table 2: Shear bond strength of adhesive system to enamel and mode of failure.

| Groups (n=20) | Shear bond strength (MPa)* | Mode of failure (ARI scores) | | | | |
|------------------|----------------------------|------------------------------|--------|--------|--------|----|
| | Mean ± SD | 1..... | 2..... | 3..... | 4..... | 5 |
| G1 | 30.14 ± 9.24 ^a | 01 | 02 | 08 | 00 | 11 |
| G2 | 15.51 ± 10.78 ^b | 01 | 02 | 02 | 01 | 14 |
| G3 | 17.77 ± 11.85 ^b | 02 | 06 | 08 | 01 | 03 |
| G4 | 28.50 ± 9.39 ^a | 02 | 01 | 03 | 02 | 12 |

◆Values with the same letter are not significantly different ($p>0.05$). SD (standard deviation). ARI (Adhesive Remaining Index); score 1: 100% adhesive on enamel; score 2: > 90% adhesives on enamel; score 3: > 10% and < 90% adhesive on enamel; score 4: < 10% adhesive on enamel; score 5: no adhesive on enamel.

used tensiometer which standardized the force applied in each bracket during bonding to the enamel, thereby differentiating of other studies that had not quantified this pressure (5,9).

For a good clinical performance, the mean adhesive strength of a material used for orthodontic appliances bonding to the enamel must be between 5.6 MPa to 7.8 MPa (23). All the groups in this study had values beyond this average. Therefore, acceptable for the orthodontic treatment.

Bond failure may occur on the surface of the bracket, the surface of the tooth or within the adhesive layer. Adhesive fractures occur at the interface of the adhesive with the bracket or enamel, whereas cohesive fractures occur inside the adhesive layer (24,25). In this study only adhesive failures were observed, probably due to bracket characteristic with a metal mesh in the base, which does not allow the adhesion between the resin/bracket interface, but only a mechanical retention on the metal mesh. The metal mesh is a ubiquitous feature of orthodontic brackets, which must be removed without causing damage to the enamel (26).

Teeth in G2 showed no remaining adhesive on the enamel (score 5), consistent with the findings reported by Patusco *et al.* (18). There was no significant difference in the ARI score distribution between G1 and G4, and the most prevalent ARI score of teeth in both groups was a score of 5. Teeth in all groups failed the SBS test, because the main purpose was to determine mode of failure (i.e. bracket debonding). Therefore, it cannot be concluded that failure necessarily occurred due to the effects of whitening. Considering the high ARI scores of teeth in G1 and G4, as well as the ideal strength values for orthodontic treatment (23), debonding in G1 and G4 was likely due to the natural limits of some property of a material involved. For example, one variable involved in the bonding that was not analyzed in this study was

the flexural strength of the resin (27). It is possible that teeth in G1 and G4 exhibited deflection of the resin or the bracket at the moment of debonding due to good mechanical retention of the resin to the metal mesh of the bracket base.

It is also important to emphasize that the direction of the force used for orthodontic bracket removal in the clinic is entirely different from the direction used in the shear test. In the mechanical test, the force was applied in the occlusal/gingival direction. In the office, the bracket is removed by a special apparatus in a perpendicular direction to the long axis of the tooth. The clinical approach maintains as much adhesive on the tooth as possible, to ensure greater control of the bracket removal process and less damage to the enamel (26).

So, as conclusion, considering the limitations of current study, bonding of the enamel/adhesive/composite/bracket system was more effective when performed 14 days after bleaching with 35% hydrogen peroxide, compared to shorter time points after bleaching.

References

1. S PM, M AB, Tejaswi S, Shetty S, K SH. Effect of power bleaching on the fluorosis stained anterior teeth case series. J Clin Diagn Res. 2014;8:ZJ01-3.
2. de Geus JL, Wambier LM, Kossatz S, Loguercio AD, Reis A. At-home vs In-office Bleaching: A Systematic Review and Meta-analysis. Oper Dent. 2016;41:341-56.
3. Cavalli V, Carvalho RM, Giannini M. Influence of carbamide peroxide-based bleaching agents on the bond strength of resin-enamel/dentin interfaces. Braz Oral Res. 2005;19:23-9.
4. Dahl JE, Pallesen U. Tooth bleaching: a critical review of the biological aspects. Crit Rev Oral Biol Med. 2003;14:292-304
5. Nascimento GC, de Miranda CA, Machado SM, Brandão GA, de Almeida HA, Silva CM. Does the time interval after bleaching influence the adhesion of orthodontic brackets? Korean J Orthod. 2013;43:242-7.
6. Bulut H, Naya AD, Turkun M. Tensile bond strength of brackets after antioxidant treatment on bleached teeth. Eur J Orthod. 2005;27:466-71.
7. Vieira C, Silva-Sousa YT, Pessarello NM, Rached-Junior FA, Sou-

- za-Gabriel AE. Effect of high-concentrated bleaching agents on the bond strength at dentin/resin interface and flexural strength of dentin. *Braz Dent J.* 2012;23:28-35.
8. Titley KC, Torneck CD, Ruse N D. The effect of carbamida peroxide gel on the shear bond strength of a microfil resin to bovine enamel. *J Dent Res.* 1992;71:20-4.
9. Akin M, Ozyilmaz OY, Yavuz T, Aykent F, Basciftci FA. Effect of Nd:YAG laser bleaching and antioxidizing agents on the shear bond strength of brackets. *Photomed Laser Surg.* 2013;31:365-70.
10. Firoozmand LM, Brandão JV, Fialho MP. Influence of microhybrid resin and etching times on bleached enamel for the bonding of ceramic brackets. *Braz Oral Res.* 2013;27:142-8.
11. Finnema KJ, Ozcan M, Post WJ, Ren Y and Dijkstra PU In-vitro orthodontic bond strength testing: A systematic review and meta-analysis. *Am J Orthod Dentofacial Orthop.* 2010;137:15-22.
12. Andrighetto AR, de Leão Withers EH, Grando KG, Ambrosio AR, Shimizu RH, Melo AC. Assessing the effects of hydrogen peroxide bleaching agent on the shear bond strength of orthodontic brackets. *Indian J Dent Res.* 2016;27:410-4.
13. Carlos LN, Jorge OS, Paranhos LR, de Freitas Vincenti SA, de Carvalho Panzeri Pires-de-Souza F. The Effect of Different Bleaching Treatments and Thermal-Mechanical Cycling on the Shear Bond Strength of Orthodontic Brackets. *Turk J Orthod.* 2018;31:110-6.
14. Olsen ME, Bishara SE, Damon P, Jakobsen JR. Evaluation of Scotchbond Multipurpose and maleic acid as alternative methods of bonding orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 1997;111:498-501.
15. Türkkahraman H, Adanir N, Güngör Y. Bleaching and Desensitizer Application Effects on Shear Bond Strengths of Orthodontic Brackets. *Angle Orthod.* 2007;77:489-93.
16. Mullins JM, Kao EC, Martin CA, Gunel E, Ngan P. Tooth whitening effects on bracket bond strength in vivo. *Angle Orthod.* 2009;79:777-83.
17. Kimyai S, Oskoe SS, Rafighi A, Valizadeh H, Ajami AA, Helali ZZ. Comparison of the effect of hydrogel and solution forms of sodium ascorbate on orthodontic bracket-enamel shear bond strength immediately after bleaching: An in vitro study. *Indian J Dent Res.* 2010;21:54-8.
18. Patusco VC, Montenegro G, Lenza MA, Carvalho AA. Bond Strength of Metallic Brackets After Dental Bleaching. *Angle Orthod.* 2009;79:122-6.
19. Oesterle LJ, Shellhart WC, Belanger GK. The use of bovine enamel in bonding studies. *Am J Orthod Dentofacial Orthop.* 1998;114:514-9.
20. Fernandes HO, Santos LB, Firoozmand LM. Shear bond strength of an orthodontic self-etching adhesive after intracoronary bleaching. *Orthod Craniofac Res.* 2015;18:117-24.
21. Uysal T, Basciftci FA, Uşümez S, Sari Z, Buyukerkmen A. Can previously bleached teeth be bonded safely? *Am J Orthod Dentofacial Orthop.* 2003;123:628-32.
22. Bishara SE, Oonsombat C, Soliman MMA, Ajlouni R, Laffon. The effect of tooth bleaching on the shear bond strength of orthodontic brackets. *Am J Orthod Dentofacial Orthop.* 2005;128:775-60.
23. Reynolds IR. A review of direct orthodontic bonding. *Br J Orthod.* 1975; 3:171-8.
24. Owens JR, Miller BH. A comparison of shear bond strengths of three visible light: cured orthodontic adhesives. *Angle Orthod.* 2000;70:352-6.
25. Katona TR. Stresses developed during clinical debonding of stainless-steel orthodontic brackets. *Angle Orthod.* 1997;67:39-46.
26. Bishara SE, VonWald L, Laffon JF; Warren JJ. Effect of a self-etch primer/adhesive on the shear bond strength of orthodontic brackets. *Am J Orthod. Dentofacial Orthop.* 2001;119:621-624.
27. Li J. Effect of flexural strength of orthodontic resin cement on bond strength of metal brackets to enamel surfaces. *Eur J Orthod.* 2011;33:167-73.

Acknowledgements

This work was partially supported by grants from Foundation for Research and Scientific and Technological Development of Maranhão – FAPEMA, process number BEPP-01294/15.

Conflict of Interests

The authors certify that they have no commercial or associative interest that represents a conflict of interest in connection with the manuscript.